



# solidian REMAT Q D4-RRE-150

Symmetrical, bidirectional reinforcement bar mats (type Q) made of media-resistant glass fiber reinforced plastic



## Material (Reinforcement bar)

Shape	Profiled round bar
Surface structure	Additive profiling
Geometry of profiling	Rib
Fiber material core	R (ECR glass)
Impregnant material	E (epoxy resin)
Color	greenish

Geometry and structure		Unit	Value	Tolerance	Standard
Direction of reinforcement bars	longitudinal	[°]	0	-	-
	transversal		90	-	
Axial distance of reinforcement bars	longitudinal	[mm]	150,0	± 3 mm	-
	transversal		150,0	± 3 mm	
Nominal diameter	longitudinal	[mm]	4,0	-	-
	transversal		4,0	-	
Outer diameter	longitudinal	[mm]	5,0	± 0,5 mm	-
	transversal		5,0	± 0,5 mm	
Static cross-sectional area of reinforcement bar	longitudinal	[mm <sup>2</sup> ]	12,57	-	-
	transversal		12,57	-	
Static cross-sectional area of reinforcement bar mat	longitudinal	[mm <sup>2</sup> /m]	83,8	-	-
	transversal		83,8	-	
Weight per meter of reinforcement bar		[g/m]	32,2	± 4 %	-
Weight per square meter of reinforcement bar mat		[g/m <sup>2</sup> ]	450	± 4 %	-
Fiber volume content		[%]	≥ 60	-	-





Material properties (Reinforcement bar)		Unit	Value	Tolerance	Standard
Bulk density of the fiber composite material		[g/cm <sup>3</sup> ]	2,16	2,14 - 2,18	ISO 1183-1
Coefficient of thermal expansion	longitudinal	[10 <sup>-6</sup> /K]	ca. 6,1	-	-
	transversal		ca. 19,5	-	
Coefficient of thermal conductivity	longitudinal	[W/(m·K)]	ca. 0,8	-	-
	transversal		ca. 0,5	-	
Glass transition temperature (DSC)		[°C]	≥ 110	-	DIN EN ISO 11357-2
Residual strength rate (alkali resistance)		[%]	≥ 70	-	ISO 10406-1
Building material class		[-]	E	-	EN 13501-1

Mechanical properties		Unit	Value	Tolerance	Standard
Average short-time tensile strength regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 1350	-	ISO 10406-1
Characteristic short-time tensile strength regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 1100	-	ISO 10406-1
Average modulus of elasticity regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 60000	-	ISO 10406-1
Characteristic elongation at break		[%]	≥ 1,83	-	ISO 10406-1
Average shear strength	longitudinal	[N/mm <sup>2</sup> ]	-	-	ISO 10406-1
	transversal	[N/mm <sup>2</sup> ]	≥ 250	-	
Characteristic short-term bond strength for ≥ C20/25		[N/mm <sup>2</sup> ]	-	-	RILEM RC6
Characteristic value of mean bond stress for w <sub>k</sub> = 0,15 mm for ≥ C20/25		[N/mm <sup>2</sup> ]	-	-	RILEM RC6
Average short-time tensile strength regarding to nominal cross-sectional area		[kN]	13,8	-	ISO 10406-1
Average short-time tensile strength regarding to nominal cross-sectional area of reinforcement mat		[kN/m]	92,0	-	-

Further characteristic values		Unit	Value	Tolerance
Cross-sectional force transmission at w <sub>k</sub> = 0,1 mm at 20°C for C50/60		[N/mm <sup>2</sup> ]	-	-

Delivery forms		Unit	Value	Tolerance
Bar mat (Standard)	Length x Width	[m]	6,0 x 2,30	-

**Storage conditions**  
Protect from weather conditions, especially from direct sunlight.



**Product page**

<https://solidian.com/products/solidian-remat/>

**build solid.**



📍 Sigmaringer Straße 150  
72458 Albstadt  
Germany - EU  
☎ +49 74 3110 3135  
✉ info@solidian.com

📍 Dr. Slavka Rozgaja 3  
47000 Karlovac  
Croatia - EU  
☎ +385 47 693 300  
✉ sales@solidian.com





## Measurement

Specified values were determined on the product itself. Deviating properties may occur in the structural component or during processing. We recommend checking the values by suitable structural component tests with the concrete formulation used in each case.

## Country-specific regulations

The use of the product is governed by the respective national regulations at the place of use, in Germany for example the building codes of the federal states, and the technical provisions based on these regulations.

The design is generally carried out in accordance with the applicable standards for reinforced concrete components, although adjustments must be made for fiber composite plastic reinforcements if applicable standards, guidelines, etc. for fiber composite plastic reinforcements are not available. Accordingly, the respective national standards and regulations must be taken into account in the design.

## Processing information

All work must be carried out by trained/instructed personnel only. Damaged fiber bundles (resin spalling, brittle areas, etc.) must not be installed, as the specified load-bearing capacity cannot be guaranteed. The specified values of the product, in particular with regard to tensile strength, only apply if the product is used as intended.

For further information, please refer to the current Technical Information for our solidian REMAT reinforcement bar mats ([www.solidian.com/downloads](http://www.solidian.com/downloads)).

## Ecology and health protection

REGULATION (EC) NO. 1907/2006 - REACH.

This product is an article as defined in Article 3 of Regulation (EC) No 1907/2006 (REACH). It does not contain substances that are released from the article during normal use. A safety data sheet according to Article 31 of the same regulation is not required to place this product on the market, to transport it or to use it. For safe use, follow the instructions from this data sheet. To our current knowledge, this product does not contain any SVHC (Substances of Very High Concern) according to Annex XIV of the REACH Regulation or substances published on the Candidate List by the European Chemicals Agency at concentrations above 0.1% (w/w).

## Industrial safety and health

Protective measures must be observed during all work with cutting equipment, such as wearing cut-resistant gloves, safety goggles and a dust mask. The actual handling of fiber composites should be based on the Technical Rules for Hazardous Substances (TRGS) of the German Federal Institute for Occupational Safety and Health (baua). Furthermore, we refer to the DGUV information "Machining of CFRP materials - Guidance for protective measures" (FB-HM 074, issue 10/2014).

## Legal information

The above information is based on our knowledge and experience under normal conditions, provided that the product has been transported, stored, used and processed properly and in accordance with the specifications in this Product Data Sheet and the Technical Information for our solidian REMAT reinforcement bar mats. The work results that can be achieved with our products depend in particular on their use and processing. The suitability of the product for the specific application must be checked in advance on your own responsibility.

Since non-metallic reinforcements are not yet regulated by building authorities in most countries, planners, specialist planners, building authorities, structural engineers, experts, etc. must be consulted for load-bearing components and country-specific regulations must be observed (e.g. approvals in individual cases).

We reserve the right to make changes to the product specifications. Third-party industrial property rights must be observed. In all other respects, our respective terms and conditions of sale and delivery shall apply. The latest technical product data sheet at the time of purchase of our products shall apply.



📍 Sigmaringer Straße 150  
72458 Albstadt

📞 +49 74 3110 3135

✉️ [info@solidian.com](mailto:info@solidian.com)

📍 Dr. Slavka Rozgaja 3  
47000 Karlovac

📞 +385 47 693 300

✉️ [sales@solidian.com](mailto:sales@solidian.com)





# solidian REMAT Q D6-RRE-150

Symmetrical, bidirectional reinforcement bar mats (type Q) made of media-resistant glass fiber reinforced plastic



## Material (Reinforcement bar)

Shape	Profiled round bar
Surface structure	Additive profiling
Geometry of profiling	Rib
Fiber material core	R (ECR glass)
Impregnant material	E (epoxy resin)
Color	greenish

Geometry and structure		Unit	Value	Tolerance	Standard
Direction of reinforcement bars	longitudinal	[°]	0	-	-
	transversal		90	-	
Axial distance of reinforcement bars	longitudinal	[mm]	150,0	± 3 mm	-
	transversal		150,0	± 3 mm	
Nominal diameter	longitudinal	[mm]	6,0	-	-
	transversal		6,0	-	
Outer diameter	longitudinal	[mm]	7,0	± 0,5 mm	-
	transversal		7,0	± 0,5 mm	
Static cross-sectional area of reinforcement bar	longitudinal	[mm <sup>2</sup> ]	28,27	-	-
	transversal		28,27	-	
Static cross-sectional area of reinforcement bar mat	longitudinal	[mm <sup>2</sup> /m]	188,47	-	-
	transversal		188,47	-	
Weight per meter of reinforcement bar		[g/m]	66,0	± 3 %	-
Weight per square meter of reinforcement bar mat		[g/m <sup>2</sup> ]	900	± 3 %	-
Fiber volume content		[%]	≥ 67	-	-



📍 Sigmaringer Straße 150  
72458 Albstadt  
Germany - EU  
☎ +49 74 3110 3135  
✉ info@solidian.com

📍 Dr. Slavka Rozgaja 3  
47000 Karlovac  
Croatia - EU  
☎ +385 47 693 300  
✉ sales@solidian.com





Material properties (Reinforcement bar)		Unit	Value	Tolerance	Standard
Bulk density of the fiber composite material		[g/cm <sup>3</sup> ]	2,16	2,14 - 2,18	ISO 1183-1
Coefficient of thermal expansion	longitudinal	[10 <sup>-6</sup> /K]	ca. 6,1	-	-
	transversal		ca. 19,5	-	
Coefficient of thermal conductivity	longitudinal	[W/(m·K)]	ca. 0,8	-	-
	transversal		ca. 0,5	-	
Glass transition temperature (DSC)		[°C]	≥ 110	-	DIN EN ISO 11357-2
Residual strength rate (alkali resistance)		[%]	≥ 75	-	ISO 10406-1
Building material class		[-]	E	-	EN 13501-1

Mechanical properties		Unit	Value	Tolerance	Standard
Average short-time tensile strength regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 1350	-	ISO 10406-1
Characteristic short-time tensile strength regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 1100	-	ISO 10406-1
Average modulus of elasticity regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 60000	-	ISO 10406-1
Characteristic elongation at break		[%]	≥ 1,83	-	ISO 10406-1
Average shear strength	longitudinal	[N/mm <sup>2</sup> ]	≥ 50	-	ISO 10406-1
	transversal	[N/mm <sup>2</sup> ]	≥ 195		
Characteristic short-term bond strength for ≥ C20/25		[N/mm <sup>2</sup> ]	-	-	RILEM RC6
Characteristic value of mean bond stress for w <sub>k</sub> = 0,15 mm for ≥ C20/25		[N/mm <sup>2</sup> ]	-	-	RILEM RC6
Average short-time tensile strength regarding to nominal cross-sectional area		[kN]	31,1	-	ISO 10406-1
Average short-time tensile strength regarding to nominal cross-sectional area of reinforcement mat		[kN/m]	207,3	-	-

Further characteristic values		Unit	Value	Tolerance
Cross-sectional force transmission at w <sub>k</sub> = 0,1 mm at 20°C for C50/60		[N/mm <sup>2</sup> ]	-	-

Delivery forms		Unit	Value	Tolerance
Bar mat (Standard)	Length x Width	[m]	6,0 x 2,30	-

**Storage conditions**  
Protect from weather conditions, especially from direct sunlight.



**Product page**

<https://solidian.com/products/solidian-remat/>

**build solid.**



📍 Sigmaringer Straße 150  
72458 Albstadt  
Germany - EU  
☎ +49 74 3110 3135  
✉ info@solidian.com

📍 Dr. Slavka Rozgaja 3  
47000 Karlovac  
Croatia - EU  
☎ +385 47 693 300  
✉ sales@solidian.com





## Measurement

Specified values were determined on the product itself. Deviating properties may occur in the structural component or during processing. We recommend checking the values by suitable structural component tests with the concrete formulation used in each case.

## Country-specific regulations

The use of the product is governed by the respective national regulations at the place of use, in Germany for example the building codes of the federal states, and the technical provisions based on these regulations.

The design is generally carried out in accordance with the applicable standards for reinforced concrete components, although adjustments must be made for fiber composite plastic reinforcements if applicable standards, guidelines, etc. for fiber composite plastic reinforcements are not available. Accordingly, the respective national standards and regulations must be taken into account in the design.

## Processing information

All work must be carried out by trained/instructed personnel only. Damaged fiber bundles (resin spalling, brittle areas, etc.) must not be installed, as the specified load-bearing capacity cannot be guaranteed. The specified values of the product, in particular with regard to tensile strength, only apply if the product is used as intended.

For further information, please refer to the current Technical Information for our solidian REMAT reinforcement bar mats ([www.solidian.com/downloads](http://www.solidian.com/downloads)).

## Ecology and health protection

REGULATION (EC) NO. 1907/2006 - REACH.

This product is an article as defined in Article 3 of Regulation (EC) No 1907/2006 (REACH). It does not contain substances that are released from the article during normal use. A safety data sheet according to Article 31 of the same regulation is not required to place this product on the market, to transport it or to use it. For safe use, follow the instructions from this data sheet. To our current knowledge, this product does not contain any SVHC (Substances of Very High Concern) according to Annex XIV of the REACH Regulation or substances published on the Candidate List by the European Chemicals Agency at concentrations above 0.1% (w/w).

## Industrial safety and health

Protective measures must be observed during all work with cutting equipment, such as wearing cut-resistant gloves, safety goggles and a dust mask. The actual handling of fiber composites should be based on the Technical Rules for Hazardous Substances (TRGS) of the German Federal Institute for Occupational Safety and Health (baua). Furthermore, we refer to the DGUV information "Machining of CFRP materials - Guidance for protective measures" (FB-HM 074, issue 10/2014).

## Legal information

The above information is based on our knowledge and experience under normal conditions, provided that the product has been transported, stored, used and processed properly and in accordance with the specifications in this Product Data Sheet and the Technical Information for our solidian REMAT reinforcement bar mats. The work results that can be achieved with our products depend in particular on their use and processing. The suitability of the product for the specific application must be checked in advance on your own responsibility.

Since non-metallic reinforcements are not yet regulated by building authorities in most countries, planners, specialist planners, building authorities, structural engineers, experts, etc. must be consulted for load-bearing components and country-specific regulations must be observed (e.g. approvals in individual cases).

We reserve the right to make changes to the product specifications. Third-party industrial property rights must be observed. In all other respects, our respective terms and conditions of sale and delivery shall apply. The latest technical product data sheet at the time of purchase of our products shall apply.





# solidian REMAT Q D8-RRE-150

Symmetrical, bidirectional reinforcement bar mats (type Q) made of media-resistant glass fiber reinforced plastic



## Material (Reinforcement bar)

Shape	Profiled round bar
Surface structure	Additive profiling
Geometry of profiling	Rib
Fiber material core	R (ECR glass)
Impregnant material	E (epoxy resin)
Color	greenish

Geometry and structure		Unit	Value	Tolerance	Standard
Direction of reinforcement bars	longitudinal	[°]	0	-	-
	transversal		90	-	
Axial distance of reinforcement bars	longitudinal	[mm]	150,0	± 3 mm	-
	transversal		150,0	± 3 mm	
Nominal diameter	longitudinal	[mm]	8,0	-	-
	transversal		8,0	-	
Outer diameter	longitudinal	[mm]	9,5	± 0,5 mm	-
	transversal		9,5	± 0,5 mm	
Static cross-sectional area of reinforcement bar	longitudinal	[mm <sup>2</sup> ]	50,27	-	-
	transversal		50,27	-	
Static cross-sectional area of reinforcement bar mat	longitudinal	[mm <sup>2</sup> /m]	335,13	-	-
	transversal		335,13	-	
Weight per meter of reinforcement bar		[g/m]	119	± 2 %	-
Weight per square meter of reinforcement bar mat		[g/m <sup>2</sup> ]	1607	± 2 %	-
Fiber volume content		[%]	≥ 67	-	-



📍 Sigmaringer Straße 150  
72458 Albstadt  
Germany - EU  
☎ +49 74 3110 3135  
✉ info@solidian.com

📍 Dr. Slavka Rozgaja 3  
47000 Karlovac  
Croatia - EU  
☎ +385 47 693 300  
✉ sales@solidian.com





Material properties (Reinforcement bar)		Unit	Value	Tolerance	Standard
Bulk density of the fiber composite material		[g/cm <sup>3</sup> ]	2,16	2,14 - 2,18	ISO 1183-1
Coefficient of thermal expansion	longitudinal	[10 <sup>-6</sup> /K]	ca. 6,1	-	-
	transversal		ca. 19,5	-	
Coefficient of thermal conductivity	longitudinal	[W/(m·K)]	ca. 0,8	-	-
	transversal		ca. 0,5	-	
Glass transition temperature (DSC)		[°C]	≥ 110	-	DIN EN ISO 11357-2
Residual strength rate (alkali resistance)		[%]	≥ 80	-	ISO 10406-1
Building material class		[-]	E	-	EN 13501-1

Mechanical properties		Unit	Value	Tolerance	Standard
Average short-time tensile strength regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 1350	-	ISO 10406-1
Characteristic short-time tensile strength regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 1100	-	ISO 10406-1
Average modulus of elasticity regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 60000	-	ISO 10406-1
Characteristic elongation at break		[%]	≥ 1,83	-	ISO 10406-1
Average shear strength	longitudinal	[N/mm <sup>2</sup> ]	≥ 50	-	ISO 10406-1
	transversal	[N/mm <sup>2</sup> ]	≥ 185		
Characteristic short-term bond strength for ≥ C20/25		[N/mm <sup>2</sup> ]	≥ 9	-	RILEM RC6
Characteristic value of mean bond stress for w <sub>k</sub> = 0,15 mm for ≥ C20/25		[N/mm <sup>2</sup> ]	≥ 6	-	RILEM RC6
Average short-time tensile strength regarding to nominal cross-sectional area		[kN]	55,3	-	ISO 10406-1
Average short-time tensile strength regarding to nominal cross-sectional area of reinforcement mat		[kN/m]	368,7	-	-

Further characteristic values		Unit	Value	Tolerance
Cross-sectional force transmission at w <sub>k</sub> = 0,1 mm at 20°C for C50/60		[N/mm <sup>2</sup> ]	-	-

Delivery forms		Unit	Value	Tolerance
Bar mat (Standard)	Length x Width	[m]	6,0 x 2,30	-

**Storage conditions**  
Protect from weather conditions, especially from direct sunlight.



**Product page**

<https://solidian.com/products/solidian-remat/>

**build solid.**



📍 Sigmaringer Straße 150  
72458 Albstadt  
Germany - EU  
☎ +49 74 3110 3135  
✉ info@solidian.com

📍 Dr. Slavka Rozgaja 3  
47000 Karlovac  
Croatia - EU  
☎ +385 47 693 300  
✉ sales@solidian.com





## Measurement

Specified values were determined on the product itself. Deviating properties may occur in the structural component or during processing. We recommend checking the values by suitable structural component tests with the concrete formulation used in each case.

## Country-specific regulations

The use of the product is governed by the respective national regulations at the place of use, in Germany for example the building codes of the federal states, and the technical provisions based on these regulations.

The design is generally carried out in accordance with the applicable standards for reinforced concrete components, although adjustments must be made for fiber composite plastic reinforcements if applicable standards, guidelines, etc. for fiber composite plastic reinforcements are not available. Accordingly, the respective national standards and regulations must be taken into account in the design.

## Processing information

All work must be carried out by trained/instructed personnel only. Damaged fiber bundles (resin spalling, brittle areas, etc.) must not be installed, as the specified load-bearing capacity cannot be guaranteed. The specified values of the product, in particular with regard to tensile strength, only apply if the product is used as intended.

For further information, please refer to the current Technical Information for our solidian REMAT reinforcement bar mats ([www.solidian.com/downloads](http://www.solidian.com/downloads)).

## Ecology and health protection

REGULATION (EC) NO. 1907/2006 - REACH.

This product is an article as defined in Article 3 of Regulation (EC) No 1907/2006 (REACH). It does not contain substances that are released from the article during normal use. A safety data sheet according to Article 31 of the same regulation is not required to place this product on the market, to transport it or to use it. For safe use, follow the instructions from this data sheet. To our current knowledge, this product does not contain any SVHC (Substances of Very High Concern) according to Annex XIV of the REACH Regulation or substances published on the Candidate List by the European Chemicals Agency at concentrations above 0.1% (w/w).

## Industrial safety and health

Protective measures must be observed during all work with cutting equipment, such as wearing cut-resistant gloves, safety goggles and a dust mask. The actual handling of fiber composites should be based on the Technical Rules for Hazardous Substances (TRGS) of the German Federal Institute for Occupational Safety and Health (baua). Furthermore, we refer to the DGUV information "Machining of CFRP materials - Guidance for protective measures" (FB-HM 074, issue 10/2014).

## Legal information

The above information is based on our knowledge and experience under normal conditions, provided that the product has been transported, stored, used and processed properly and in accordance with the specifications in this Product Data Sheet and the Technical Information for our solidian REMAT reinforcement bar mats. The work results that can be achieved with our products depend in particular on their use and processing. The suitability of the product for the specific application must be checked in advance on your own responsibility.

Since non-metallic reinforcements are not yet regulated by building authorities in most countries, planners, specialist planners, building authorities, structural engineers, experts, etc. must be consulted for load-bearing components and country-specific regulations must be observed (e.g. approvals in individual cases).

We reserve the right to make changes to the product specifications. Third-party industrial property rights must be observed. In all other respects, our respective terms and conditions of sale and delivery shall apply. The latest technical product data sheet at the time of purchase of our products shall apply.



📍 Sigmaringer Straße 150  
72458 Albstadt

Germany - EU

☎ +49 74 3110 3135

✉ [info@solidian.com](mailto:info@solidian.com)

📍 Dr. Slavka Rozgaja 3  
47000 Karlovac

Croatia - EU

☎ +385 47 693 300


✉ [sales@solidian.com](mailto:sales@solidian.com)





# solidian REMAT Q D10-RRE-150

Symmetrical, bidirectional reinforcement bar mats (type Q) made of media-resistant glass fiber reinforced plastic

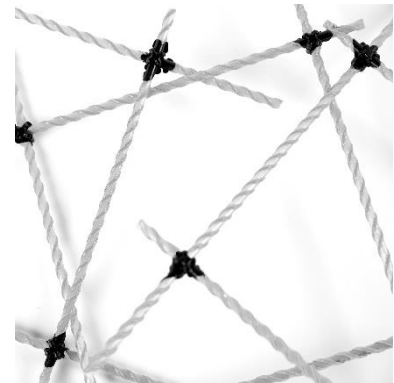

## Material (Reinforcement bar)

Shape	Profiled round bar
Surface structure	Additive profiling
Geometry of profiling	Rib
Fiber material core	R (ECR glass)
Impregnant material	E (epoxy resin)
Color	greenish

## Geometry and structure

		Unit	Value	Tolerance	Standard
Direction of reinforcement bars	longitudinal	[°]	0	-	-
	transversal		90	-	
Axial distance of reinforcement bars	longitudinal	[mm]	150,0	± 3 mm	-
	transversal		150,0	± 3 mm	
Nominal diameter	longitudinal	[mm]	10,0	-	-
	transversal		10,0	-	
Outer diameter	longitudinal	[mm]	11,5	± 0,5 mm	-
	transversal		11,5	± 0,5 mm	
Static cross-sectional area of reinforcement bar	longitudinal	[mm <sup>2</sup> ]	78,54	-	-
	transversal		78,54	-	
Static cross-sectional area of reinforcement bar mat	longitudinal	[mm <sup>2</sup> /m]	523,6	-	-
	transversal		523,6	-	
Weight per meter of reinforcement bar		[g/m]	177	± 2 %	-
Weight per square meter of reinforcement bar mat		[g/m <sup>2</sup> ]	2380	± 2 %	-
Fiber volume content		[%]	≥ 67	-	-



📍 Sigmaringer Straße 150  
72458 Albstadt  
Germany - EU  
☎ +49 74 3110 3135  
✉ info@solidian.com

📍 Dr. Slavka Rozgaja 3  
47000 Karlovac  
Croatia - EU  
☎ +385 47 693 300  
✉ sales@solidian.com





Material properties (Reinforcement bar)		Unit	Value	Tolerance	Standard
Bulk density of the fiber composite material		[g/cm <sup>3</sup> ]	2,14	2,12 - 2,16	ISO 1183-1
Coefficient of thermal expansion	longitudinal	[10 <sup>-6</sup> /K]	ca. 6,1	-	-
	transversal		ca. 19,5	-	
Coefficient of thermal conductivity	longitudinal	[W/(m·K)]	ca. 0,8	-	-
	transversal		ca. 0,5	-	
Glass transition temperature (DSC)		[°C]	≥ 110	-	DIN EN ISO 11357-2
Residual strength rate (alkali resistance)		[%]	≥ 80	-	ISO 10406-1
Building material class		[-]	E	-	EN 13501-1

Mechanical properties		Unit	Value	Tolerance	Standard
Average short-time tensile strength regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 1200	-	ISO 10406-1
Characteristic short-time tensile strength regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 1050	-	ISO 10406-1
Average modulus of elasticity regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 55000	-	ISO 10406-1
Characteristic elongation at break		[%]	≥ 1,91	-	ISO 10406-1
Average shear strength	longitudinal	[N/mm <sup>2</sup> ]	≥ 50	-	ISO 10406-1
	transversal	[N/mm <sup>2</sup> ]	≥ 180		
Characteristic short-term bond strength for ≥ C20/25		[N/mm <sup>2</sup> ]	≥ 9	-	RILEM RC6
Characteristic value of mean bond stress for w <sub>k</sub> = 0,15 mm for ≥ C20/25		[N/mm <sup>2</sup> ]	≥ 6	-	RILEM RC6
Average short-time tensile strength regarding to nominal cross-sectional area		[kN]	82,5	-	ISO 10406-1
Average short-time tensile strength regarding to nominal cross-sectional area of reinforcement mat		[kN/m]	550,0	-	-

Further characteristic values		Unit	Value	Tolerance
Cross-sectional force transmission at w <sub>k</sub> = 0,1 mm at 20°C for C50/60		[N/mm <sup>2</sup> ]	ca. 100	-

Delivery forms		Unit	Value	Tolerance
Bar mat (Standard)	Length x Width	[m]	6,0 x 2,30	-

**Storage conditions**  
Protect from weather conditions, especially from direct sunlight.



**Product page**

<https://solidian.com/products/solidian-remat/>

**build solid.**

Date: 01.03.2023 | Version: 2303 | solidian REMAT Q D10-RRE-150 Technical Product Data Sheet v2303.docx

Page 2



📍 Sigmaringer Straße 150  
72458 Albstadt  
Germany - EU

☎ +49 74 3110 3135

✉ info@solidian.com

📍 Dr. Slavka Rozgaja 3  
47000 Karlovac  
Croatia - EU

☎ +385 47 693 300

✉ sales@solidian.com





## Measurement

Specified values were determined on the product itself. Deviating properties may occur in the structural component or during processing. We recommend checking the values by suitable structural component tests with the concrete formulation used in each case.

## Country-specific regulations

The use of the product is governed by the respective national regulations at the place of use, in Germany for example the building codes of the federal states, and the technical provisions based on these regulations.

The design is generally carried out in accordance with the applicable standards for reinforced concrete components, although adjustments must be made for fiber composite plastic reinforcements if applicable standards, guidelines, etc. for fiber composite plastic reinforcements are not available. Accordingly, the respective national standards and regulations must be taken into account in the design.

## Processing information

All work must be carried out by trained/instructed personnel only. Damaged fiber bundles (resin spalling, brittle areas, etc.) must not be installed, as the specified load-bearing capacity cannot be guaranteed. The specified values of the product, in particular with regard to tensile strength, only apply if the product is used as intended.

For further information, please refer to the current Technical Information for our solidian REMAT reinforcement bar mats ([www.solidian.com/downloads](http://www.solidian.com/downloads)).

## Ecology and health protection

REGULATION (EC) NO. 1907/2006 - REACH.

This product is an article as defined in Article 3 of Regulation (EC) No 1907/2006 (REACH). It does not contain substances that are released from the article during normal use. A safety data sheet according to Article 31 of the same regulation is not required to place this product on the market, to transport it or to use it. For safe use, follow the instructions from this data sheet. To our current knowledge, this product does not contain any SVHC (Substances of Very High Concern) according to Annex XIV of the REACH Regulation or substances published on the Candidate List by the European Chemicals Agency at concentrations above 0.1% (w/w).

## Industrial safety and health

Protective measures must be observed during all work with cutting equipment, such as wearing cut-resistant gloves, safety goggles and a dust mask. The actual handling of fiber composites should be based on the Technical Rules for Hazardous Substances (TRGS) of the German Federal Institute for Occupational Safety and Health (baua). Furthermore, we refer to the DGUV information "Machining of CFRP materials - Guidance for protective measures" (FB-HM 074, issue 10/2014).

## Legal information

The above information is based on our knowledge and experience under normal conditions, provided that the product has been transported, stored, used and processed properly and in accordance with the specifications in this Product Data Sheet and the Technical Information for our solidian REMAT reinforcement bar mats. The work results that can be achieved with our products depend in particular on their use and processing. The suitability of the product for the specific application must be checked in advance on your own responsibility.

Since non-metallic reinforcements are not yet regulated by building authorities in most countries, planners, specialist planners, building authorities, structural engineers, experts, etc. must be consulted for load-bearing components and country-specific regulations must be observed (e.g. approvals in individual cases).


We reserve the right to make changes to the product specifications. Third-party industrial property rights must be observed. In all other respects, our respective terms and conditions of sale and delivery shall apply. The latest technical product data sheet at the time of purchase of our products shall apply.





# solidian REMAT Q D12-RRE-150

Symmetrical, bidirectional reinforcement bar mats (type Q) made of media-resistant glass fiber reinforced plastic

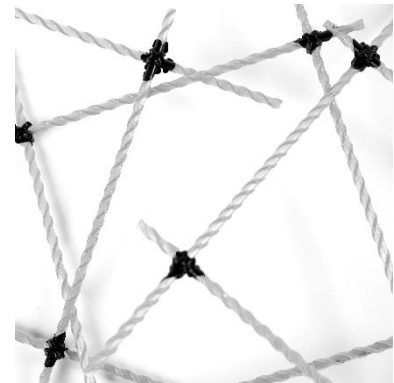

## Material (Reinforcement bar)

Shape	Profiled round bar
Surface structure	Additive profiling
Geometry of profiling	Rib
Fiber material core	R (ECR glass)
Impregnant material	E (epoxy resin)
Color	greenish

Geometry and structure		Unit	Value	Tolerance	Standard
Direction of reinforcement bars	longitudinal	[°]	0	-	-
	transversal		90	-	
Axial distance of reinforcement bars	longitudinal	[mm]	150,0	± 3 mm	-
	transversal		150,0	± 3 mm	
Nominal diameter	longitudinal	[mm]	12,0	-	-
	transversal		12,5	-	
Outer diameter	longitudinal	[mm]	13,5	± 0,5 mm	-
	transversal		13,5	± 0,5 mm	
Static cross-sectional area of reinforcement bar	longitudinal	[mm <sup>2</sup> ]	113,10	-	-
	transversal		113,10	-	
Static cross-sectional area of reinforcement bar mat	longitudinal	[mm <sup>2</sup> /m]	754,0	-	-
	transversal		754,0	-	
Weight per meter of reinforcement bar		[g/m]	257	± 2 %	-
Weight per square meter of reinforcement bar mat		[g/m <sup>2</sup> ]	3447	± 2 %	-
Fiber volume content		[%]	≥ 67	-	-



📍 Sigmaringer Straße 150  
72458 Albstadt  
Germany - EU  
☎ +49 74 3110 3135  
✉ info@solidian.com

📍 Dr. Slavka Rozgaja 3  
47000 Karlovac  
Croatia - EU  
☎ +385 47 693 300  
✉ sales@solidian.com





Material properties (Reinforcement bar)		Unit	Value	Tolerance	Standard
Bulk density of the fiber composite material		[g/cm <sup>3</sup> ]	2,14	2,12 - 2,16	ISO 1183-1
Coefficient of thermal expansion	longitudinal	[10 <sup>-6</sup> /K]	ca. 6,1	-	-
	transversal		ca. 19,5	-	
Coefficient of thermal conductivity	longitudinal	[W/(m·K)]	ca. 0,8	-	-
	transversal		ca. 0,5	-	
Glass transition temperature (DSC)		[°C]	≥ 110	-	DIN EN ISO 11357-2
Residual strength rate (alkali resistance)		[%]	≥ 80	-	ISO 10406-1
Building material class		[-]	E	-	EN 13501-1

Mechanical properties		Unit	Value	Tolerance	Standard
Average short-time tensile strength regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 1200	-	ISO 10406-1
Characteristic short-time tensile strength regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 1050	-	ISO 10406-1
Average modulus of elasticity regarding to nominal cross-sectional area		[N/mm <sup>2</sup> ]	≥ 55000	-	ISO 10406-1
Characteristic elongation at break		[%]	≥ 1,91	-	ISO 10406-1
Average shear strength	longitudinal	[N/mm <sup>2</sup> ]	≥ 47	-	ISO 10406-1
	transversal	[N/mm <sup>2</sup> ]	≥ 170		
Characteristic short-term bond strength for ≥ C20/25		[N/mm <sup>2</sup> ]	≥ 9	-	RILEM RC6
Characteristic value of mean bond stress for w <sub>k</sub> = 0,15 mm for ≥ C20/25		[N/mm <sup>2</sup> ]	≥ 6	-	RILEM RC6
Average short-time tensile strength regarding to nominal cross-sectional area		[kN]	118,8	-	ISO 10406-1
Average short-time tensile strength regarding to nominal cross-sectional area of reinforcement mat		[kN/m]	792,0	-	-

Further characteristic values		Unit	Value	Tolerance
Cross-sectional force transmission at w <sub>k</sub> = 0,1 mm at 20°C for C50/60		[N/mm <sup>2</sup> ]	ca. 90	-

Delivery forms		Unit	Value	Tolerance
Bar mat (Standard)	Length x Width	[m]	6,0 x 2,30	-

**Storage conditions**  
Protect from weather conditions, especially from direct sunlight.



**Product page**

<https://solidian.com/products/solidian-remat/>

**build solid.**



📍 Sigmaringer Straße 150  
72458 Albstadt  
Germany - EU

☎ +49 74 3110 3135

✉ info@solidian.com

📍 Dr. Slavka Rozgaja 3  
47000 Karlovac  
Croatia - EU

☎ +385 47 693 300

✉ sales@solidian.com



## Measurement

Specified values were determined on the product itself. Deviating properties may occur in the structural component or during processing. We recommend checking the values by suitable structural component tests with the concrete formulation used in each case.

## Country-specific regulations

The use of the product is governed by the respective national regulations at the place of use, in Germany for example the building codes of the federal states, and the technical provisions based on these regulations.

The design is generally carried out in accordance with the applicable standards for reinforced concrete components, although adjustments must be made for fiber composite plastic reinforcements if applicable standards, guidelines, etc. for fiber composite plastic reinforcements are not available. Accordingly, the respective national standards and regulations must be taken into account in the design.

## Processing information

All work must be carried out by trained/instructed personnel only. Damaged fiber bundles (resin spalling, brittle areas, etc.) must not be installed, as the specified load-bearing capacity cannot be guaranteed. The specified values of the product, in particular with regard to tensile strength, only apply if the product is used as intended.

For further information, please refer to the current Technical Information for our solidian REMAT reinforcement bar mats ([www.solidian.com/downloads](http://www.solidian.com/downloads)).

## Ecology and health protection

REGULATION (EC) NO. 1907/2006 - REACH.

This product is an article as defined in Article 3 of Regulation (EC) No 1907/2006 (REACH). It does not contain substances that are released from the article during normal use. A safety data sheet according to Article 31 of the same regulation is not required to place this product on the market, to transport it or to use it. For safe use, follow the instructions from this data sheet. To our current knowledge, this product does not contain any SVHC (Substances of Very High Concern) according to Annex XIV of the REACH Regulation or substances published on the Candidate List by the European Chemicals Agency at concentrations above 0.1% (w/w).

## Industrial safety and health

Protective measures must be observed during all work with cutting equipment, such as wearing cut-resistant gloves, safety goggles and a dust mask. The actual handling of fiber composites should be based on the Technical Rules for Hazardous Substances (TRGS) of the German Federal Institute for Occupational Safety and Health (baua). Furthermore, we refer to the DGUV information "Machining of CFRP materials - Guidance for protective measures" (FB-HM 074, issue 10/2014).

## Legal information

The above information is based on our knowledge and experience under normal conditions, provided that the product has been transported, stored, used and processed properly and in accordance with the specifications in this Product Data Sheet and the Technical Information for our solidian REMAT reinforcement bar mats. The work results that can be achieved with our products depend in particular on their use and processing. The suitability of the product for the specific application must be checked in advance on your own responsibility.

Since non-metallic reinforcements are not yet regulated by building authorities in most countries, planners, specialist planners, building authorities, structural engineers, experts, etc. must be consulted for load-bearing components and country-specific regulations must be observed (e.g. approvals in individual cases).

We reserve the right to make changes to the product specifications. Third-party industrial property rights must be observed. In all other respects, our respective terms and conditions of sale and delivery shall apply. The latest technical product data sheet at the time of purchase of our products shall apply.



📍 Sigmaringer Straße 150  
72458 Albstadt

Germany - EU

☎ +49 74 3110 3135

✉ [info@solidian.com](mailto:info@solidian.com)

📍 Dr. Slavka Rozgaja 3  
47000 Karlovac

Croatia - EU

☎ +385 47 693 300

✉ [sales@solidian.com](mailto:sales@solidian.com)

